Low-energy magnetic excitations in the quasi-one-dimensional spin-1 chain compound $SrNi_2V_2O_8$

Zhe Wang,[1] M. Schmidt,[1] A. K. Bera,[2] A. T. M. N. Islam,[2] B. Lake,[2,3] A. Loidl,[1] and J. Deisenhofer[1]

[1] *Experimental Physics V, Center for Electronic Correlations and Magnetism, Institute of Physics, University of Augsburg, D-86135 Augsburg, Germany*
[2] *Helmholtz-Zentrum Berlin für Materialien und Energie, D-14109 Berlin, Germany*
[3] *Institut für Festkörperphysik, Technische Universität Berlin, D-10623 Berlin, Germany*

(Dated: January 1, 2013)

Multi-frequency electron spin resonance (ESR) and time-domain transmission spectra have been measured as function of temperature and magnetic field on single crystals of the quasi-one-dimensional spin-1 chain compound $SrNi_2V_2O_8$ in the GHz to THz frequency range. Magnetic resonance modes above 50 K have been observed with an effective g-factor of 2.24 at 100 K. Below 30 K, intra-triplet excitations have been observed in the ESR spectra, which reveal the presence of single-ion anisotropy with $D = -0.29$ meV.

PACS numbers: 78.30.Am,75.10.pq,71.70.-d

arXiv:1212.6859v1 [cond-mat.str-el] 31 Dec 2012

I. INTRODUCTION

The one-dimensional spin-1 system with nearest-neighbor Heisenberg antiferromagnetic exchange J exhibits a magnetic excitation gap, *i.e.* the Haldane gap, $\Delta = 0.41J$ between a spin-singlet ground state and a spin-triplet excited state.[1–3] The effects of interchain exchange interactions $J_\perp$ and single-ion anisotropy D on the ground state and excitation gap have been extensively studied in various theoretical approaches.[4–8] An ideal one-dimensional spin-1 system does not have long-range order above $T = 0$ K due to strong spin fluctuations, and only when sufficiently large interchain exchange interactions exist, long-range order can form at finite temperature. The magnetic excitation gap can be reduced or completely suppressed with the presence of interchain exchange interaction and single-ion anisotropy.[4–8]

The isotructural spin-chain compounds $ANi_2V_2O_8$ (A = Pb and Sr) based on Ni^{2+} ions with $S = 1$ have attracted considerable attention[9–15] because the excitation gap ($0.23J$ for A = Pb,[9] and $0.25J$ for A = Sr[15]) is significantly smaller than the expected $\Delta = 0.41J$. This indicates that these compounds are close to a phase boundary in the D–$J_\perp$ phase diagram.[7] $ANi_2V_2O_8$ crystallizes in tetragonal symmetry with space group $I4_1cd$, where the edge-shared NiO_6 octahedra surrounding the fourfold screw axis form screw chains along the c-axis [Fig. 1(a)(b)].[15] The magnetic susceptibility of $ANi_2V_2O_8$ increases with decreasing temperature and exhibits a broad maximum around 130 K [see Fig. 1(c) for $SrNi_2V_2O_8$], which is characteristic for a spin-1 Haldane system.[9,15] There are no anomalies observed down to 1.9 K, which indicates a nonmagnetic singlet ground state of these compounds.[9,12,14,15] By slightly doping at the Ni-site or the A-site with nonmagnetic ions, the ground state changes from a disordered spin-liquid state to a Néel ordered state.[9,11,14] This disorder-to-order transition has been ascribed to the modification on the interchain exchange interaction by substitution.

Based on a perturbative approach to describe inelastic neutron scattering results,[8] the single-ion anisotropy in $PbNi_2V_2O_8$ and $SrNi_2V_2O_8$ has been estimated as -0.45 and -0.56 meV, respectively.[10] An ESR study reported a smaller value of about -0.31 meV for $PbNi_2V_2O_8$,[13] in agreement with an estimate from magnetization measurements.

In this work, we investigate the excitation spectra of $SrNi_2V_2O_8$ single crystals in the GHz to THz frequency range by time-domain transmission spectroscopy and multi-frequency ESR transmission spectroscopy. We have observed the intra-triplet excitations in the ESR spectra. The analysis of the field dependence of the intra-triplet excitation spectra reveals the existence of significant single-ion anisotropy in $SrNi_2V_2O_8$.

II. EXPERIMENTAL DETAILS

Single crystals of $SrNi_2V_2O_8$ were grown by the floating zone technique, the details of which will be published elsewhere.[16] Magnetic susceptibility was measured with a constant magnetic field of 1 T parallel to the a-axis in the warming cycle from 2 to 400 K using a Quantum Design physical properties measurement system. The single crystals for optical measurements were oriented by Laue diffraction and cut perpendicular to the a-axis with dimension of $2 \times 2 \times 1$ mm^3 and perpendicular to the c-axis with $2 \times 2 \times 0.7$ mm^3. Time-domain THz transmission measurements were carried out for $5 < T < 300$ K using a TPS Spectra 3000 spectrometer (TeraView Ltd.). Multi-frequency transmission experiments were performed for $2 < T < 210$ K with an applied magnetic field varying up to 7 T in Voigt configuration for the external magnetic field $\mathbf{H}$ parallel to the a-axis ($\mathbf{H} \parallel a$) and the c-axis ($\mathbf{H} \parallel c$) with backward-wave oscillators covering the frequency range 125 - 500 GHz and a magneto-optical cryostat (Oxford/Spectromag).

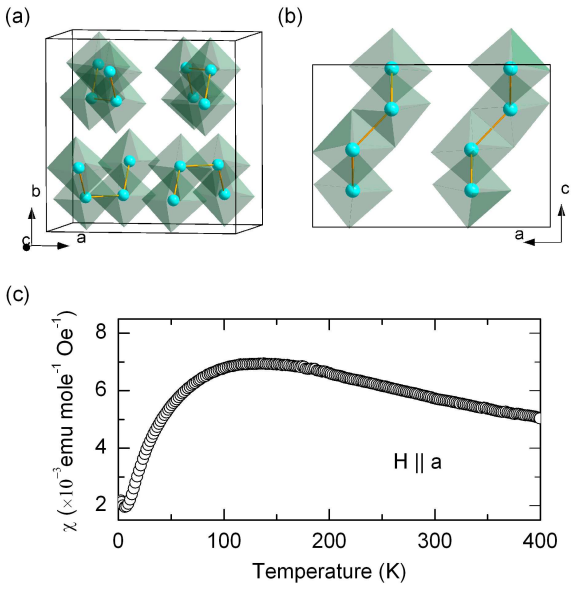

FIG. 1: (Color online) (a) Edge-shared NiO_6 octahedra surrounding the fourfold screw axis forming spin chains along the c-axis in a unit cell of $SrNi_2V_2O_8$. Ni ions are shown by the spheres. (b) Two spin chains along the c-axis. (c) Temperature dependence of the magnetic susceptibility measured at 1 T with the magnetic field parallel to the a-axis.

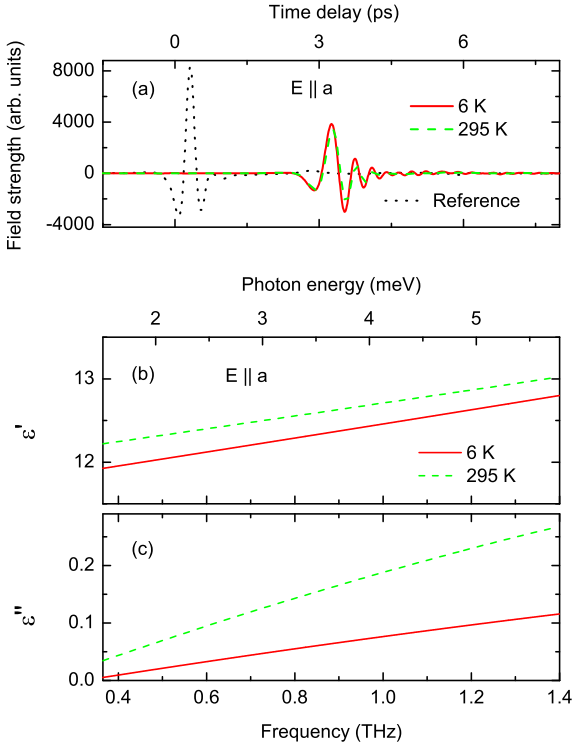

FIG. 2: (Color online) (a) Field transient as a function of time-delay measured at 6 K and 295 K. (b) Dielectric constant and (c) dielectric loss as a function of frequency obtained at 6 K and 295 K.

III. EXPERIMENTAL RESULTS AND DISCUSSIONS

A. Time-domain THz transmission spectroscopy

The polarization dependence of the transmission has been measured with the radiation electric field parallel to the a-axis and the c-axis. Figure 2(a) shows the field transient as a function of time-delay measured on the 0.7 mm-thick crystal with the radiation electric field parallel to the a-axis ($\mathbf{E} \parallel a$). The transmission increases slightly at 6 K as compared to the one at room temperature.

Transmission and phase in frequency domain can be obtained by Fourier transformation, which enable us to determine the dielectric functions. The obtained dielectric constant ε' and dielectric loss ε'' [see Figs. 2(b) and (c)], which decrease slightly with decreasing temperature. The dielectric constant is around 12.5 and almost frequency-independent in the corresponding frequency range. The dielectric loss of $SrNi_2V_2O_8$ is below 0.3 and almost zero in the low frequency limit. Neutron experiments have revealed magnetic excitation gaps in the energy range from 1.65 to 4 meV (about from 0.40 to 0.97 THz) at different Brillouin zone centers.[16] In our transmission measurements, we have not observed any absorption bands corresponding to these gaps either for $\mathbf{E} \parallel a$ or for $\mathbf{E} \parallel c$. As a spin-1 chain compound, the spin Hamiltonian of $SrNi_2V_2O_8$ is mainly composed of intra- and inter-chain exchange interactions, and single-ion anisotropy. The singlet-triplet excitations are usually forbidden when only symmetric exchange interactions and single-ion anisotropy are dominant. The absence of these excitations in the THz spectra indicate that the antisymmetric Dzyaloshinskii-Moriya exchange interaction between the spins of Ni^{2+} ions, which was proposed to be responsible for the previously reported long-range order in $SrNi_2V_2O_8$,[10] is too weak to provide a significant admixture between singlet and triplet states.[17–19]

B. Multifrequency ESR transmission spectroscopy

Figures 3(a) and (b) show the transmission as a function of magnetic field measured at 155 GHz for various temperatures above 50 K for $\mathbf{H} \parallel c$ and $\mathbf{H} \parallel a$, respectively. At 207 K, a resonance mode is observed at 4.73 T for $\mathbf{H} \parallel c$ corresponding to an exchange-narrowed Ni^{2+} ESR signal, as marked by the arrow in Fig. 3(a). The resonance field increases with decreasing temperature and reaches 5.27 T at 69 K. Below 50 K this mode cannot be resolved. As shown in Fig. 3(b), the resonance mode can be also observed above 50 K for $\mathbf{H} \parallel a$. The temperature dependence is consistent with the isostructural compound $PbNi_2V_2O_8$.[13] The transmission spectra as a function of magnetic field corresponding to several frequencies have been measured for $\mathbf{H} \parallel c$ and for $\mathbf{H} \parallel a$.

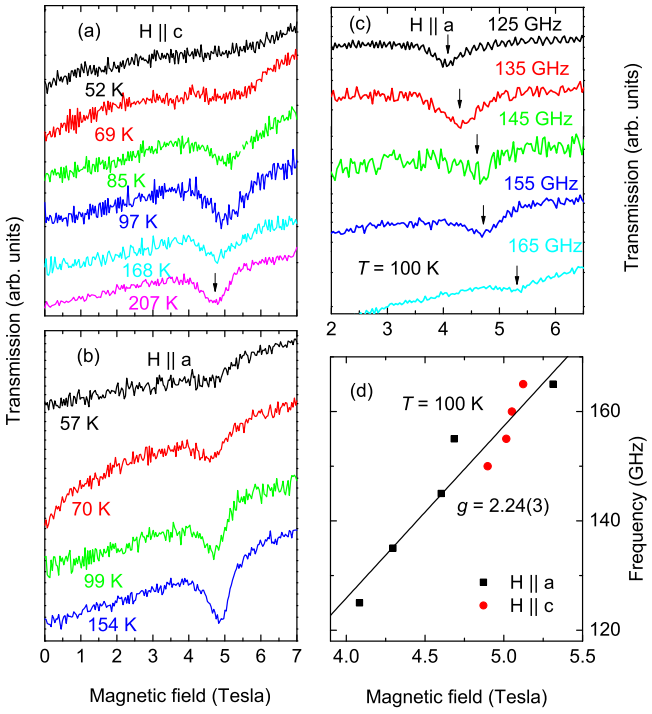

FIG. 3: (Color online) Transmission spectra at 155 GHz measured for various temperature with the magnetic field (a) parallel to the c-axis and (b) parallel to the a-axis. (c) Transmission spectra at various frequencies measured for 100 K with $\mathbf{H} \parallel a$. (d) Resonance frequency as a function of resonance field at 100 K. Linear fit gives a g-factor of 2.24(3).

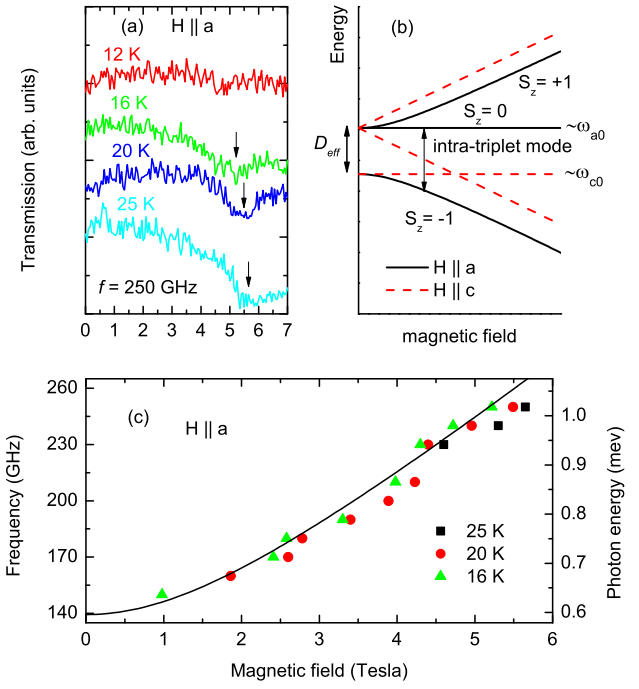

FIG. 4: (Color online) (a) Transmission spectra of 250 GHz measured at various temperatures with $\mathbf{H} \parallel a$. (b) Zeeman splitting scheme of spin-triplet states for $\mathbf{H} \parallel a$ (solid lines) and $\mathbf{H} \parallel c$ (dashed lines) according to the macroscopic field theory.[13,21] (c) Resonance frequencies versus resonance magnetic fields determined from various spectra measured at various temperatures with $\mathbf{H} \parallel a$. The line is a fit of the data obtained at 16 K according to the Eq. (1) given by the macroscopic field theory.

Fig. 3(c) shows the transmission spectra at 100 K at various frequencies with $\mathbf{H} \parallel a$, which reveal resonance modes as marked by the arrows. The resonance modes have also been observed in the transmission spectra for $\mathbf{H} \parallel c$ (not shown). The observed resonance frequencies versus resonance magnetic fields at 100 K are shown in Fig. 3(d). The field dependence of resonance frequencies exhibits a linear relation corresponding to the paramagnetic resonance. The experimental data can be fitted by a linear function through the origin resulting in a g-factor of 2.24(3) for both field orientations. The line in Fig. 3(d) shows the fit result that is in good agreement with the experimental data. The obtained g-factor is consistent with 2.23 determined in $PbNi_2V_2O_8$,[11,13] which is a typical value for Ni^{2+} ions in octahedral crystal fields.[20]

The intensity of the ESR modes shown in Figs. 3(a) and (b) increases slightly with decreasing temperature and then decreases significantly below 100 K. This is consistent with the temperature dependence of the magnetic susceptibility, which exhibits a broad maximum around 130 K [see Fig. 1(c)]. At low temperatures, the ESR modes are quite broad, have low intensity, and cannot be tracked below 50 K.

Figure 4(a) shows the transmission spectra at 250 GHz measured below 30 K for $\mathbf{H} \parallel a$. A new absorption mode around 5.5 T can be seen at 25 K. The resonance field of this mode decreases slightly with decreasing temperature. This mode cannot be resolved when the temperature is below 12 K. We assign this mode to the intra-triplet resonance mode of Ni^{2+} ions [see Fig. 4(b)]. At very low temperatures (below 12 K), the lower-lying triplet branch becomes much less populated due to the magnetic gap, therefore the intra-triplet excitations cannot be observed. Below 30 K, the splitting of spin-triplet state has also been observed in the inelastic neutron scattering experiments.[16] We did not observe any mode in the transmission spectra at 250 GHz measured in the same temperature range for $\mathbf{H} \parallel c$ (not shown), which indicates that a significant single-ion anisotropy exists in this compound.[8,13]

The single-ion anisotropy contributes to the Hamiltonian in the form $D(S_i^z)^2$ with the anisotropy constant $D < 0$ (easy-axis type), which gives rise to the zero-field splitting of the spin-triplet state. Theoretically, an effective anisotropy $D_{eff} \equiv -1.98D$ corresponding to the intra-triplet splitting in spin-1 systems has been studied[8] and applied to explain the results of $PbNi_2V_2O_8$.[13] With the presence of single-ion anisotropy, the dependence of triplet states on the external magnetic field is quite different for $\mathbf{H} \parallel c$ and for $\mathbf{H} \parallel a$ [see Fig. 4(b)].[8,13] For

$D_{eff} > 0$, the state $|S_z = -1\rangle$ ($|-1\rangle$) is the lower-lying state of the three split states for $\mathbf{H} \parallel a$, while the state $|S_z = 0\rangle$ ($|0\rangle$) has lowest energy for $\mathbf{H} \parallel c$ when the magnetic field is smaller than 4.4 T (estimated from D_{eff}, see below). Consequently, the most probable intra-triplet excitations will be from $|-1\rangle$ to $|0\rangle$ for $\mathbf{H} \parallel a$ and from $|0\rangle$ to $|\pm 1\rangle$ for $\mathbf{H} \parallel c$. With increasing magnetic field, the absorption mode corresponding to $|-1\rangle \rightarrow |0\rangle$ for $\mathbf{H} \parallel a$ will have more intensity and shifts to higher frequency due to the lowering of the energy of the $|-1\rangle$ state by the Zeeman contribution. However, the intensity corresponding to $|0\rangle \rightarrow |\pm 1\rangle$ is rather constant for $\mathbf{H} \parallel c$ since the population of the $|0\rangle$ state will not be altered by the magnetic field.

The resonance frequencies versus resonance fields of the observed modes for $\mathbf{H} \parallel a$ are plotted in Fig. 4(c). Below 1 T, we cannot resolve any modes due to the low population of the $|-1\rangle$ state. This is consistent with the fact that no modes corresponding to $|0\rangle \rightarrow |\pm 1\rangle$ can be resolved from the spectra for $\mathbf{H} \parallel c$, which should have lower intensity compared to $|-1\rangle \rightarrow |0\rangle$ for $\mathbf{H} \parallel a$. According to the macroscopic field theory,[13,21] the field dependence of the frequency difference between the states $|0\rangle$ and $|-1\rangle$ for $\mathbf{H} \parallel a$ can be described by

$$\omega(H) = \sqrt{A+B} - \sqrt{(\gamma H)^2 + A - \sqrt{B^2 + 4A(\gamma H)^2}} \quad (1)$$

where $\gamma = g\mu_B$ with μ_B the Bohr magneton, $A \equiv \frac{\omega_{a0}^2+\omega_{c0}^2}{2}$ and $B \equiv \frac{\omega_{a0}^2-\omega_{c0}^2}{2}$ with ω_{a0} the eigenfrequency of the $|0\rangle$ state for $\mathbf{H} \parallel a$ and ω_{c0} the eigenfrequency of the $|0\rangle$ state for $\mathbf{H} \parallel c$ [see Fig. 4(b)].

As shown by the solid line in Fig. 4(c), the fit to the experimental data at 16 K with Eq. (1) provides a good description of the experimental results, where we use a g-factor of 2.24. The fit determines the intra-triplet splitting $\omega_{a0} - \omega_{c0}$ of 139 GHz at zero magnetic field corresponding to $D_{eff} = 0.57$ meV. Consequently, the single-ion anisotropy D can be estimated as -0.29 meV, which is close to -0.4 meV determined at 16 K by the inelastic neutron scattering experiments.[16]

IV. CONCLUSION

The absence of singlet-triplet excitations in the zero-field transmission spectra indicates that the admixture between the spin singlet and triplet states induced by the Dzyaloshinskii-Moriya interaction is not significant in $SrNi_2V_2O_8$. Multi-frequency electron spin resonance transmission spectra have been measured as a function of temperature on single crystalline $SrNi_2V_2O_8$ with the external magnetic field parallel and perpendicular to the spin-chain direction. Above 50 K, the exchange-narrowed Ni^{2+} paramagnetic resonance lines have been observed, which determines a g-factor of 2.24(3) at 100 K. Between 10 and 30 K, intra-triplet resonance lines are observed for $\mathbf{H} \parallel a$ but not for $\mathbf{H} \parallel c$ in the same frequency range. The difference between different orientations of external magnetic field indicates the existence of single-ion anisotropy, which is estimated as -0.29 meV.

Acknowledgments

We acknowledge partial support by the Deutsche Forschungsgemeinschaft via TRR 80 (Augsburg-Munich) and Project DE 1762/2-1.

[1] F. D. M. Haldane, Phys. Lett. **93A**, 464 (1983).
[2] F. D. M. Haldane, Phys. Rev. Lett. **50**, 1153 (1983)
[3] S. R. White, Phys. Rev. Lett. 69, 2863 (1992); S. R. White and D. A. Huse, Phy. Rev. B **48**, 3844 (1993); S. R. White and I. Affleck, *ibid.* **77**, 134437 (2008).
[4] R. Botet and R. Jullien, Phys. Rev. B **27**, 613 (1983).
[5] J. B. Parkinson and J. C. Bonner, Phys. Rev. B 32, 4703 (1985).
[6] M. P. Nightingale and H. W. J. Blöte, Phys. Rev. B 33, 659 (1986).
[7] T. Sakai and M. Takahashi, Phys. Rev. B **42**, 4537 (1990).
[8] O. Golinelli, Th. Jolicœur, and R. Lacaze, J. Phys.: Condens. Matter **5**, 7847 (1993).
[9] Y. Uchiyama, Y. Sasago, I. Tsukada, K. Uchinokura, A. Zheludev, T. Hayashi, N. Miura, and P. Böni, Phys. Rev. Lett. **83**, 632 (1999).
[10] A. Zheludev, T. Masuda, I. Tsukada, Y. Uchiyama, K. Uchinokura, P. Böni, and S.-H. Lee, Phys. Rev. B **62**, 8921 (2000).
[11] A. I. Smirnov, V. N. Glazkov, H.-A. Krug von Nidda, A. Loidl, L. N. Demianets, and A. Ya. Shapiro, Phys. Rev. B **65**, 174422 (2002).
[12] B. Pahari, K. Ghoshray, R. Sarkar, B. Bandyopadhyay, and A. Ghoshray, Phys. Rev. B **73**, 012407 (2006).
[13] A. I. Smirnov, V. N. Glazkov, T. Kashiwagi, S. Kimura, M. Hagiwara, K. Kindo, A. Ya. Shapiro, and L. N. Demianets, Phys. Rev. B **77**, 100401(R) (2008).
[14] Z. He and Y. Ueda, J. Phys. Soc. Jpn., **77** 013703, (2008)
[15] A. K. Bera and S. M. Yusuf, Phys. Rev. B **86**, 024408 (2012).
[16] A. K. Bera *et. al.*, unpublished.
[17] M. Matsumoto, T. Shoji, and M. Koga, J. Phys. Soc. Jpn. **77**, 074712 (2008).
[18] Z. Wang, M. Schmidt, A. Günther, S. Schaile, N. Pascher, F. Mayr, Y. Goncharov, D. L. Quintero-Castro, A. T. M. N. Islam, B. Lake, H.-A. Krug von Nidda, A. Loidl, and J. Deisenhofer, Phys. Rev. B **83**, 201102 (2011).
[19] Z. Wang, M. Schmidt, Y. Goncharov, Y. Skourski, J. Wosnitza, H. Berger, H.-A. Krug von Nidda, A. Loidl, J. Deisenhofer, J. Phys. Soc. Jpn. **80**, 124707 (2011)
[20] A. Abragam and B. Bleaney, *Electron Paramagnetic Resonance of Transition Ions*, Clarendon Press, Oxford (1970).
[21] A. M. Farutin and V. I. Marchenko, Journal of Experimental and Theoretical Physics **104**, 751 (2007).